

## High Density Polyethylene



# HM10561

EVALENE<sup>®</sup> HM10561 is a High Density Polyethylene resin designed specifically for rope, net and related applications.

**EVALENE<sup>®</sup> HM10561** offers advantages in net, rope and filament applications through improved stretchability resulting in higher stretch ratios and improved tenacities. As a versatile grade, it is also used in select flexible packaging and injection-molded applications.

### FEATURES

- Good throughputs
- Excellent balance of tenacity and stretchability
- Meets Philippine FDA food contact requirements
- Halal-certified

### TYPICAL APPLICATIONS

- Commercial and industrial ropes and nets (fishing net, agricultural net, mosquito net)
- Non-woven filament applications

## Product Properties


Property	Test Condition	Method	Typical Value	Unit
Melt Index	190°C / 2.16kg	ASTM D1238	1.0	g/10 min.
Density	23°C	ASTM D1505	956	kg/m <sup>3</sup>
Tensile Strength at Yield*	50 mm/min	ASTM D638	26	MPa
Tensile Strength at Break*	50 mm/min	ASTM D638	20	MPa
Elongation at Yield*	50 mm/min	ASTM D638	21	%
Elongation at Break*	50 mm/min	ASTM D638	1119	%
Tensile Modulus	1% Secant, 5 mm/min	ASTM D638	1274	MPa
Flexural Modulus	1% Secant, 1.3 mm/min	ASTM D790	715	MPa

\*Tensile properties tested using ASTM Type I Injection molded samples

### Typical Processing Conditions:

Extrusion temperature: 230 - 260 °C

### Resin Property Comparison: EVALENE® HM10561 and other HDPE monofilament grade

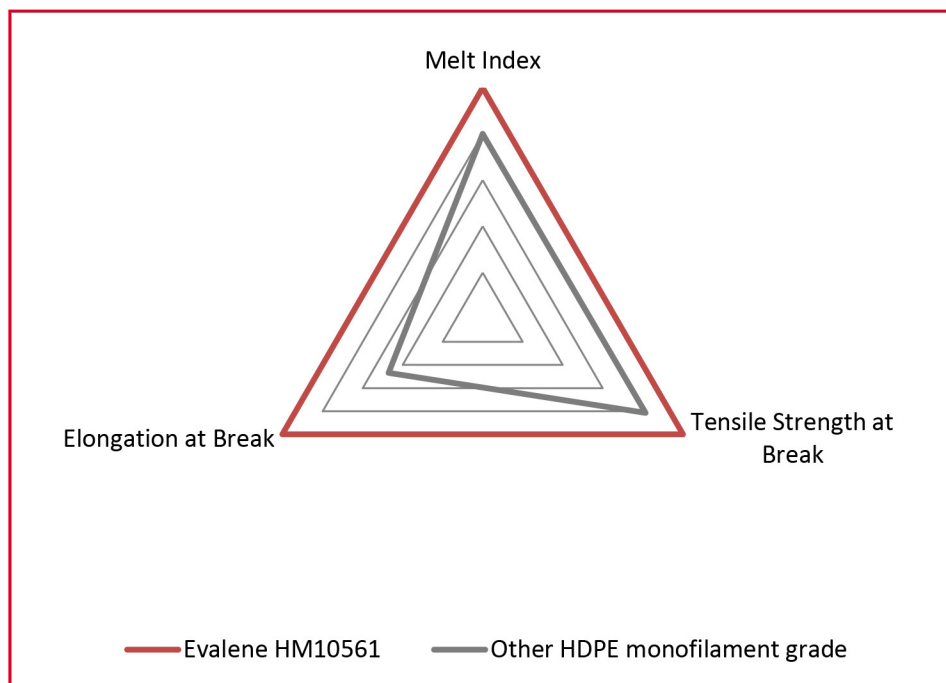

**EVALENE® HM10561's** higher melt index results in (1) higher extruder throughputs for the same extrusion temperatures or (2) less energy requirement for the same extruder throughput.

**EVALENE® HM10561's** higher elongation and tensile strength at break allow for stretch ratios with corresponding higher tenacities.

#### Disclaimer:

Information provided herein is given for general purposes only. It is the customer's sole responsibility to test the product and any information provided herein to determine whether they are suitable for the customer's purposes. JGSPC MAKES NO REPRESENTATIONS OR WARRANTIES, EITHER EXPRESS OR IMPLIED, OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE OR OF ANY OTHER NATURE ARE MADE HEREUNDER WITH RESPECT TO INFORMATION OR THE PRODUCT TO WHICH INFORMATION REFERS. Customers are strongly advised to review the applicable Material Safety Data Sheet before handling or using the products described herein.



Find out more about us at:  
[www.jgspetrochem.com](http://www.jgspetrochem.com)